
Forces Perspective of Drillability of Titanium Alloy 6Al-2Sn-4Zr-6Mo

Mahros Darsin^a, Tim Pasang^b, Zhan Chen^c

^a Department of Mechanical Engineering, University of Jember
Jalan Kalimantan 37 Jember 68121, Indonesia
+62 331 410243
e-mail: mahros.teknik@unej.ac.id

^{b,c} Department of Mechanical Engineering, Auckland University of Technology
55 Wellesley Street, Auckland 1010, New Zealand
+64 9 921 9999
e-mail: timotius.pasang@aut.ac.nz & zhan.chen@aut.ac.nz

Abstract

This paper concerns on drillability of Ti-6Al-2Sn-4Zr-6Mo (Ti-6246) from the point view of thrust force (Fz) & torque (Mz) using a TiAlN CVD coated carbide tool. The condition of the material was varied with three different heat treatments. Whereas, the machining parameters were varied in cutting speed, feed rate and cooling application method. Taguchi method L-18 was employed to design the experiments. Both type of forces, thrust force and torque, were measured using a Kistler dynamometer, and the data were analyzed using a Minitab 17 software. The thrust force was influenced by the cutting speed 24%, depth of drilling 21%, heat treatment 13%, and feed rate 11%. The torque was influenced predominantly by feed rate up to 94%. Coolant application has no effect on reducing both thrust force as well as torque.

Keywords: Ti-6246; drillability; Taguchi method; force; torque

1. INTRODUCTION

Drillability term is derived from machinability, which means how easy the material be drilled with a drill bit. This paper discusses drillability of titanium alloy 6Al-2Sn-4Zr-6Mo when being drilled with TiAlN-coated carbide from forces point of view. Cutting forces is a measure of machinability. Normally, it is desired the lower cutting forces. In drilling, an elevated cutting force can arouse the vibration of the spindle axis, consequently resulting in low quality of drilled surface. It may also cause premature devastation of drills and lessen the tool life. An elevated temperature at the interface of tool-workpiece may be produced when the torque was increased due to friction between tool and workpiece [1]. There is a close connection between forces that work during drilling with the surface quality [2]. Therefore, it is interesting to study drillability from the forces point of view.

In drilling, there are two different motions: cutting speed and feed rate. Cutting speed makes the tool cut the workpiece only once of full rotation and feed rate provides the continuity of drilling process. Torque is the force that make the drill able to rotate along vertical axis; it relates to cutting speed. While, thrust force is the force that make the drill move along vertical axis (Z-axis) and it relates to feed rate.

Titanium alloy 6Al-2Sn-4Zr-6Mo (Ti-6246) is among alpha + beta titanium alloys. It has excellent corrosion ratio than the most famous titanium alloy, Ti-6Al-4V, therefore, it is potentially applied for sea water medium and high chemical influent working area also for deep & sour-well applications. It is heat treatable and designed to combine the strength properties at long term elevated temperature of Ti-6Al-2Sn-4Zr-2Mo-0.08 Si with the high developed short term strength properties of fully hardened alpha + beta alloy. Hence, it possibly for forging parts which receive withstand high at intermediate temperature such as turbine blades, compressor disks and airframe components.

Some previous researchers have observed relation of forces that works during machining titanium alloys and the machining parameters. Cutting force (F_c) and feed force (F_f) have been discussed on machining three kind of titanium alloys Ti-6Al4V, Ti-54M and Ti-10.2.3 with variation in machining parameters. They concluded that feed rate was the most influential factor which affects the forces [3]. Laser assisted machining (LAM) has reduced the forces up to maximum 15% in compare to conventional machining of Ti-6Cr-5Mo-5V-4Al [4]. There is also some published paper on drilling titanium which focus on cutting forces. The main forces that work drilling (thrust force and torque) were greatly affected by the type of coolant used [5,6]. Thrust force decreased as cutting speed increased but a lower torque values were obtained at the higher cutting speed applied [7]. Other researchers concerned on effect of drilling technique on forces as reviewed on Sharif et al. [6]. Literatures studied show that there is no published paper discussing drillability of titanium alloy 6Al-2Sn-4Zr-6Mo especially from forces point view. Therefore, this study worth to value.

2. METHODS

The material used were titanium alloy 6246 in form of 56 mm - rod with the nominal chemical composition in compare to the result of OES (optical emission spectroscopy) is presented in Table 2.1.

Table 2.1 Taguchi method L-18 design experiments, the forces and S/R ratio

Work Material Ti-6Al-2Sn-4Zr-6Mo	Alloying elements, wt.%				Impurity limits, wt.% max				
	Al	Sn	Zr	Mo	N	C	H	Fe	O
From literature [8] ⁸	6	2	4	6	0.04	0.04	0.0125	0.15	0.15
OES Test Result	6.69	2.18	4.09	5.85		0.012		0.062	

In advance of drilling, the workpiece was machined to shape rectangular blocks according to the depth of the proposed drilling and to fit with the fixture, width x length = 25 x 25 mm; the heights were varied as 15, 35 and 50 mm according to the proposed depth of drilling 10, 30 and 45 mm respectively. The workpiece was then fastened in a fixture. The fixture itself was mounted on a Kistler piezoelectric dynamometer to measure the forces that worked during drilling. The recorded forces were displayed and recorded in a PC outside the CNC. Four forces were recorded, i.e. F_x , F_y , F_z and M_z .

Five parameters were varied to get the optimum value of forces. Three parameters from drilling ones: cutting force, feed rate, depth of drilling. One variation made from the block being drilled: heat treatments. Another variation came from the environment, i.e. whether drilling with or without coolant. Each variation of parameters has 3 levels except for the coolant application method, only two levels. The experiments were carried out according to Taguchi method L-18 to reduce the number of experiments [9,10] ^{9,10}. The recorded forces then would be analysed with Minitab 17 and analysis of variance (ANOVA) for checking the significance of each parameters. The variations or level of each parameters is presented in Table 2.2. The initial of AR in heat treatment row means that the material was drilled as-received condition. While HT1 represent heat treatment at 870°C for 3 hours following by furnace cooling and HT2 denotes heat treatment at 870°C for 3 hours followed by water quenching. Both heat treatments were chosen based on the preliminary research which result in decreasing the hardness compare to as-received. The value of the hardness of AR, HT1 and HT2 was 318, 311 and 289 HV respectively. Lessening the hardness hopefully result in easier to machine. The coolant (coolant 'on') is a synthetic coolant to water ratio 1:10 of HOCUT 795B made by Houghton Australia with flood method at flow rate of 0.02 l/s through a nozzle. The low and high level of both cutting speed and feed rate were chosen according to the specification of the drill manufacturer for drilling titanium. Hence, the variation of depth of drilling was made because the typical application of this material is for thick parts. The drill insert was denoted as IC908 SumoCham of TiAlN PVD coated carbide.

Table 2.2 Variation of drilling parameters and their level

Machining Parameters	Level		
	Low	Medium	High
Coolant	Off	-	On
Heat Treatment	AR	HT1	HT2
Depth of drilling (mm)	10	30	45
Cutting speed (m/min)	27	35	50
Feed rate (mm/rev)	0.08	0.11	0.15

3. RESULTS AND DISCUSSION

3.1 Results

A photo of a moment after drilling showing of the drill and the block as well as the dynamometer is presented in Fig.3.1. The recorded forces (F_x , F_y , F_z and M_z) then being plotted as a graph using Microsoft Excel program. The average of F_x and F_y were around zero value, therefore both were abandoned in further analysis and only F_z (thrust force) and M_z (torque around the vertical axis) were considered. For analysis in Minitab 17, the forces were sorted out from only at the steady state then take the average as illustrated in Fig. 3.2. The steady state indicating that the tool was fully engage in drilling process [11]¹¹. The increase of forces in the graph may relate to tool deterioration.

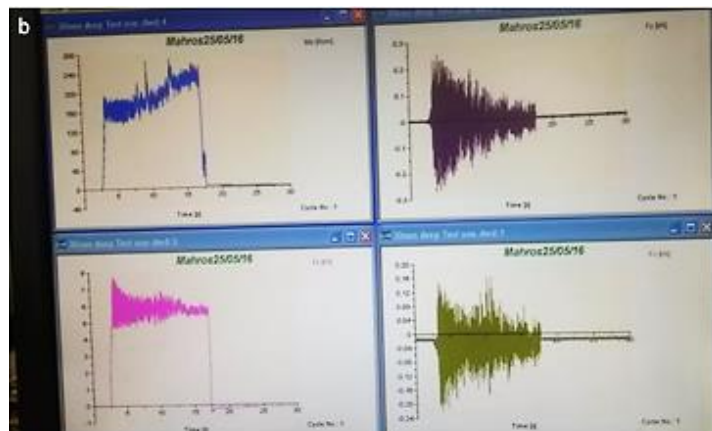


Fig. 3.1 Images showing (a) a moment after a complete drilling, (b) appearance of forces measurement in a PC monitor in the CCW direction from the upper right: F_y , F_x , F_z , and M_z

The completed average of thrust force (Fz) and torque (Mz) is presented in Table 3.1 along the calculated signal to noise ratio (S/N ratio). The calculation of S/N ratio was based on minimization because the smaller forces are preferable, as the following formula³:

$$\left[\frac{S}{N} \right]_{LB} = -10 \log \left(\frac{1}{n} \sum_{i=1}^n y_i^2 \right) \quad (1)$$

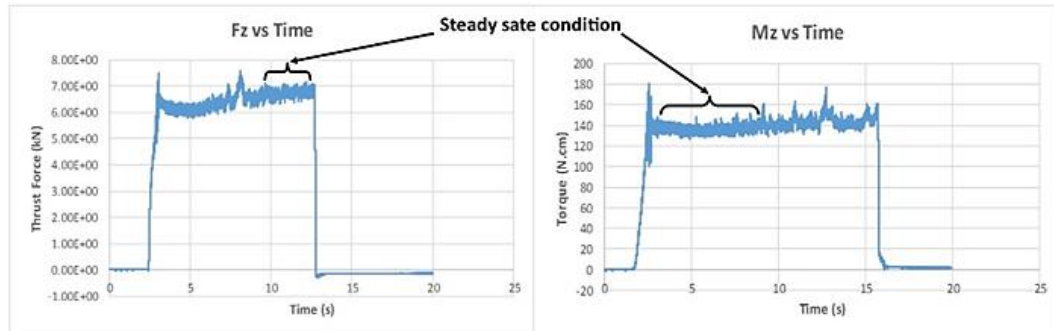


Fig. 3.2. Illustration how the average thrust force and torque were calculated from the steady state condition

Table 3.1 Taguchi method L-18 design experiments, the forces and S/R ratio

Exp	Control variables					Average of responses		S/N ratio (dB)	
	Coo-lant	HT	h (mm)	Vc (m/min)	Fr (mm/rev)	Fz (N)	Mz (N.cm)	Fz	Mz
1	No	AR	10	27	0.08	2638	147	-68.43	-43.35
2	No	AR	30	35	0.11	5762	165	-75.21	-44.33
3	No	AR	45	50	0.15	3567	227	-71.05	-47.10
4	No	HT1	10	27	0.11	2679	171	-68.56	-44.66
5	No	HT1	30	35	0.15	6701	215	-76.52	-46.64
6	No	HT1	45	50	0.08	2234	135	-66.98	-42.63
7	No	HT2	10	35	0.08	2245	139	-67.02	-42.86
8	No	HT2	30	50	0.11	6761	164	-76.60	-44.31
9	No	HT2	45	27	0.15	2744	200	-68.77	-46.01
10	Yes	AR	10	50	0.15	3895	235	-71.81	-47.42
11	Yes	AR	30	27	0.08	5256	143	-74.41	-43.12
12	Yes	AR	45	35	0.11	7231	171	-77.18	-44.67
13	Yes	HT1	10	35	0.15	3064	210	-69.73	-46.44
14	Yes	HT1	30	50	0.08	2260	137	-67.08	-42.72
15	Yes	HT1	45	27	0.11	2735	167	-68.74	-44.43
16	Yes	HT2	10	50	0.11	2761	180	-68.82	-45.11
17	Yes	HT2	30	27	0.15	2037	207	-66.18	-46.32
18	Yes	HT2	45	35	0.08	5225	128	-74.36	-42.12

3.2 Discussion

ANOVA analyses was used to detect which factors affecting the forces. A confidence level 95% (or significance level of $\alpha = 0.05$) was used to carry out the critical analysis. The ANOVA of thrust force and torque were presented in Table 3.2 & Table 3.3. The factor with the P-values less than 0.05 means statistically significant at 95% confidence level and vice

versa [3]. Whereas, the larger the F-value for certain parameter the bigger the effect on the characteristic of performance due to change in that process parameter [3].

Table 3.2 Analysis of variance for thrust force

Source	DF	Adj SS	Adj MS	F-Value	P-Value	Contribution, %
Coolant	1	41762	41762	0.02	0.892	0
HT	2	6829219	3414609	1.62	0.257	13
h	2	11065125	5532562	2.62	0.133	21
Vc	2	13077118	6538559	3.10	0.101	24
Fr	2	5823134	2911567	1.38	0.306	11
Error	8	16896812	2112102			31
Total	17	53733170				

Table 3.3 Analysis of variance for torque

Source	DF	Adj SS	Adj MS	F-Value	P-Value	Contribution, %
Coolant	1	13.3	13.28	0.46	0.518	0
HT	2	446.8	223.38	7.69	0.014	2
h	2	315.5	157.75	5.43	0.032	2
Vc	2	249.4	124.69	4.29	0.054	1
Fr	2	18164.6	9082.29	312.82	0	94
Error	8	232.3	29.03			1
Total	17	19421.7				

From Table 3.2 it is clear that each factor contributed in affecting the thrust force in order are 24% by cutting speed, 21% by depth of drilling, 13% by heat treatment and 11% by feed rate. In contrast, torque was predominantly affected feed rate up to 94% (Table 3.3). While other machining parameters influence cumulatively about 6% toward the torque. The result is in accordance with what was found by Khanna in Davim [12] that feed rate contribute 97.2% on cutting force. Some previous researchers in drilling Al7075 using Response Surface Methodology (RSM) found that increase cutting speed did not result in increase of Fz and Mz (Kyratsis et al. in Davim [12]), while increase feed rate and tool diameter would increase both forces in drilling. The difference result may due to difference material used. Another research on drilling on titanium using RSM design experiment shown that cutting force and feed rate both were significantly affecting thrust force and torque [13]. It is also evidence that cutting fluid does not play a role in affecting both forces. It may due to the method of applying coolant in this experiment – an external coolant supply - was not effective. The coolant could not reach the tool-chips interface therefore there was no different in forces whether drilling with or without coolant application. A compressive flood coolant application might help to reduce the forces during drilling as claimed by Rahim & Sasahara [5]. There was a difference up to 1000 N of thrust force between MQL synthetic ester and flood coolant while torque difference up to 11 N.m.

An important note in interpreting of experimental analysis, if the percent contribution due to error (unknown and uncontrolled factors) is low, 15% or less, then it is assumed that no important factors were omitted from the experiments. If it is high value, 50% or more, then some important factors were definitely omitted, conditions were not precisely controlled, or measurement error was excessive [14]. In case of ANOVA result of thrust force, the error is 31%, it means some factors that may influenced the thrust force are omitted from the experiments. However, the error is less than 50% or it is still acceptable.

The next step is analysis to find the optimum forces that may works by varying the machining parameters. The S/N ratio of Table 3.3 and 3.4 of both thrust and torque then being plotted as shown in Fig 3.3. Signal to noise ratio indicates how the controlled parameters (signal) affecting the measured result in compare to disturbance (noise or uncontrolled parameters). Therefore, the higher S/N ratio is preferable. From Fig. 3.4 we can detect that the optimum thrust force would be achieved by choosing machining with coolant and the material being HT1 treated on drilling depth of 10 mm, cutting speed of 27 m/min and feed rate 0.08 mmm/rev. While, minimum torque would be achieved when drilling without coolant, material as HT2, depth of drilling 45 mm, cutting speed at 35 m/min and feed rate of 0.08 mm/rev.

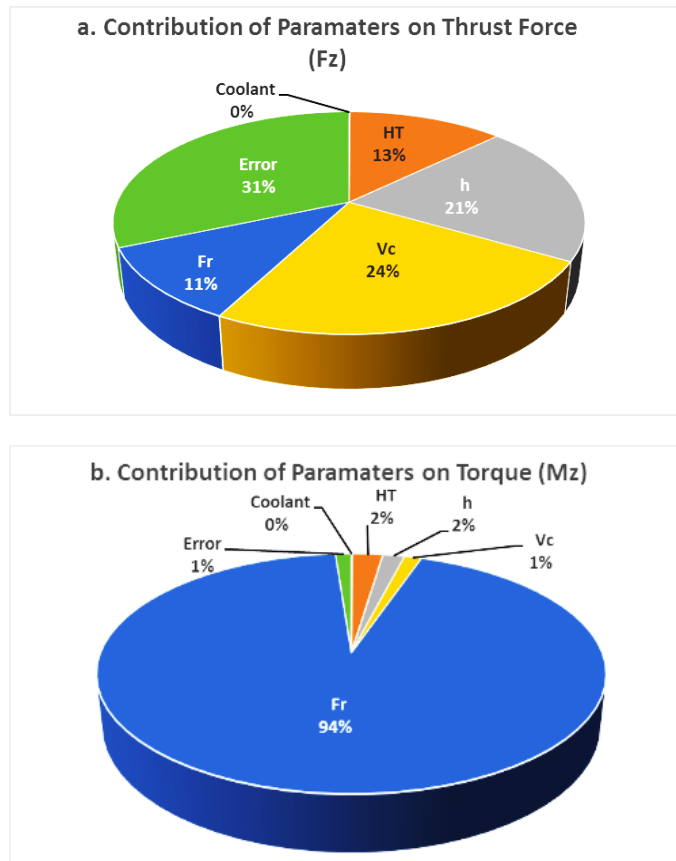


Fig. 3.3. Contribution of each factors to the thrust force (a) and to the torque (b)

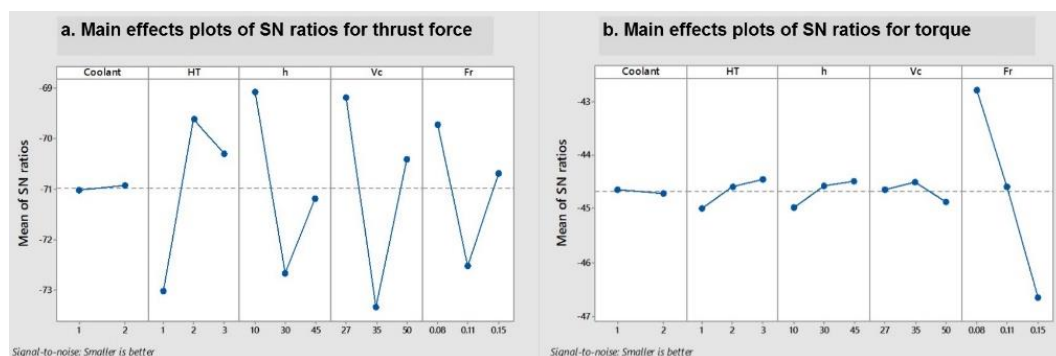


Fig. 3.4. Means of forces and S/N effect for each control factor; (a) thrust force, (b) torque.

Both forces require different level of parameters in order to achieve their minimum values. Therefore, we should smartly decide which one we should choose. As mentioned previously that application of coolant would not change significantly to thrust and torque, together with environment consideration, the drilling without coolant may be chosen. Furthermore, as feed rate predominantly affecting the torque we may abandon the level of three other factors and follow the ones which result the minimum thrust force. Thus, optimum thrust force and torque may be achieved by applying V_c of 27m/min, F_r of 0.08 mm/rev on depth of 10 mm on material at HT1 without coolant.

4. CONCLUSION

Following the result and discussion, we may come to conclusion regarding drillability of Ti-6Al-2Sn-4Zr-6Mo from the forces point of view:

- a. Among five parameters that varied: cutting speed, depth of drilling, heat treatment and feed rate influenced the thrust force by order in percentage as 24, 21, 13, and 11 respectively. While torque was greatly influenced by feed rate up to 94%. Applying of coolant did not contribute in reducing the drilling forces.
- b. The optimum drilling forces condition would be achieved when drilling with cutting speed of 27 m/min, feed rate of 0.08 m/rev on depth of only 10 mm without coolant while material should be HT1 treated.

The further reduction in forces may be gained either by applying high pressure coolant or using the through coolant tool design.

ACKNOWLEDGMENT

We would like to thank Ministry of Research, Technology and Higher Education of Republic Indonesia through the DIKTI scholarship that financially supports the main author to pursue his PhD degree at the Auckland University of Technology. We would like also appreciate the Auckland University of Technology that support for the funding after third year passed.

REFERENCES

1. Zhang, P. F.; Churi, N. J.; Pei, Z. J.; and Treadwell, C. (2008). Mechanical drilling processes for titanium alloys: a literature review. *Machining Science Technology*, 12(4):417-444.
2. Pirtini, M.; and Lazoglu, I. (2005). Forces and hole quality in drilling. *International Journal Machine Tools & Manufacture*, 45(11), 1271-1281.
3. Khanna, N; and Davim, J. P. (2015). Design-of-experiments application in machining titanium alloys for aerospace structural components. *Measurement*, 61, 280-290.
4. Rashid, R. A.; Sun, S.; Wang, G.; and Dargusch, M. S. (2012). An investigation of cutting forces and cutting temperatures during laser-assisted machining of the Ti-6Cr-5Mo-5V-4Al beta titanium alloy. *International Journal Machine Tools & Manufacture*, 63, 58-69.
5. Rahim, E. A.; and Sasahara, H. 2011. A study of the effect of palm oil as MQL lubricant on high speed drilling of titanium alloys. *Tribology International*, 44(3), 309-317.
6. Sharif, S.; Rahim, E. A.; and Sasahara, H. (2012). Machinability of Titanium Alloys in Drilling, *Titanium Alloys - Towards Achieving Enhanced Properties for Diversified Applications*, Nurul Amin, A. K. M. (Ed.), InTech.
7. Rahim, E.A.; Kamdani, K.; and Sharif, S. (2008). Performance Evaluation of Uncoated Carbide Tool in High Speed Drilling of Ti6Al4V. *Journal of Advanced Mechanical Design, Systems, and Manufacturing*, 2(4):522-531.
8. Lutjering, G.; and Williams, J. C. (2007). *Titanium*. 2nd ed. (Derby B, ed.). Springer-Verlag BerlinHeidelberg.
9. Youssef, Y. A.; Beauchamp Y. and Thomas, M. (1994). Comparison of a full factorial experiment to fractional and taguchi designs in a lathe dry turning operation. *Computers & Industrial Engineering*, 27(1-4):59-62.

10. Islam, M. N.; and Pramanik, A. (2016). Comparison of Design of Experiments via Traditional and Taguchi Method. *Journal of Advanced Manufacturing Systems*,15(3):151-160.
11. Neto, N. F. M. (2017). Orbital drilling of Titanium alloys for aeronautics applications. Experimental studies. Master's Dissertation, Universidade Do Porto, Portugal.
12. Davim, J. P. (2016). *Design of Experiments in Production Engineering*. Springer International Publishing Switzerland.
13. Chatterjee, S.; Mahapatra, S. S.; and Abhishek, K. (2016). Simulation and optimization of machining parameters in drilling of titanium alloys. *Simulation Modelling Practice and Theory*, 62 (2016) 31–48.
14. Ross, P. J. (1988). *Taguchi Method for Quality Engineering*. Mc Graw Hill Company